


# Improving battery life for wearable electronic devices by addressing asymmetric stresses

August 25 2020

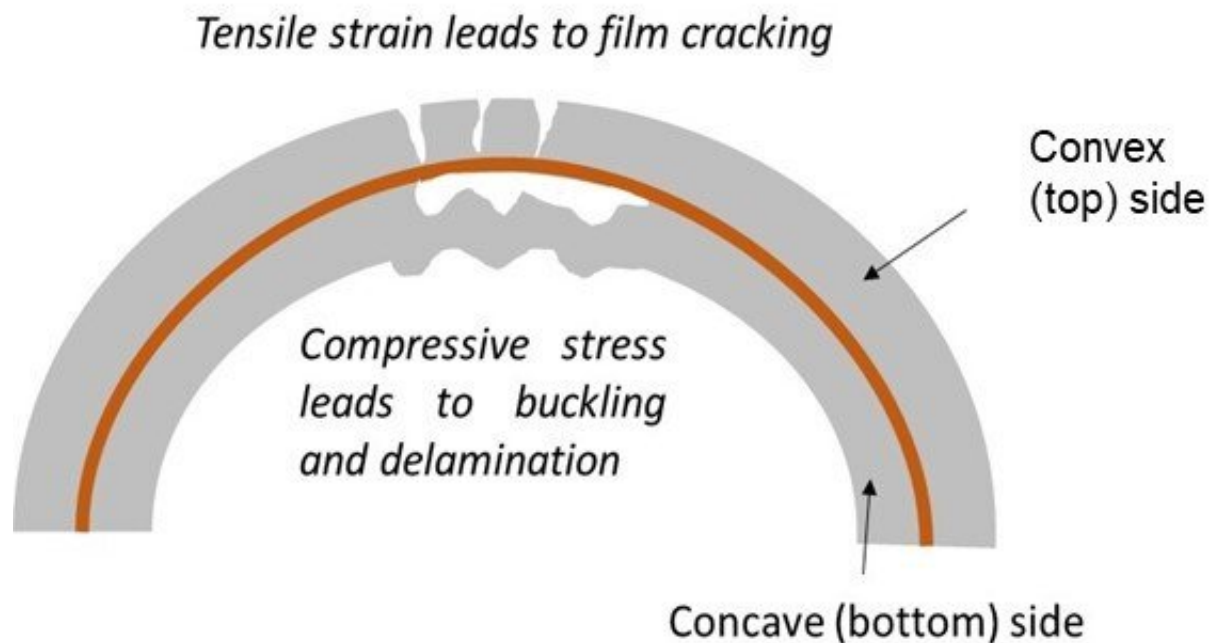





A diagram of how tensile strain leads to the film cracking. Credit: University of Warwick

Researchers in WMG and the Department of Physics at the University of Warwick have found that asymmetric stresses within electrodes used in certain wearable electronic devices provides an important clue as to how to improve the durability and lifespan of these batteries.

Batteries for [medical applications](#) and wearable devices continue to evolve in size and shape, with miniaturization of Li-ion technologies becoming increasingly popular. However, as the size of the battery shrinks, the fabrication process for composite electrodes and the use of liquid electrolyte is becoming a processing challenge for microfabrication using conventional approaches.

Lithium cobalt oxide  $\text{LiCoO}_2$  (LCO) has remained a common choice of cathode for these small formats due to its high voltage platform and energy density. However, following the initial reported performance benefits of LCO, it is known that LCO cells have large impedance issues due to the growth of high surface layer resistance and charge transfer resistance. This can affect how efficiently the battery charges and discharges. There are also ethical and health considerations around the use of the element cobalt. The increasing impedance was thought to be attributable to the growth of a surface layer on both the anode (solid electrolyte interface, SEI) and cathode (cathode electrolyte interface, CEI) due to the reaction between the electrodes and the electrolyte.

However, in the paper "Aging analysis and asymmetric stress considerations for small format cylindrical cells for [wearable electronic devices](#)" published recently in the *Journal of Power Sources*, the University of Warwick's WMG and Physics department researchers disassembled these cells. They have found that the condition of the cathode and anode varied greatly after 500 cycles, as a function of which side of the current collector it was on.

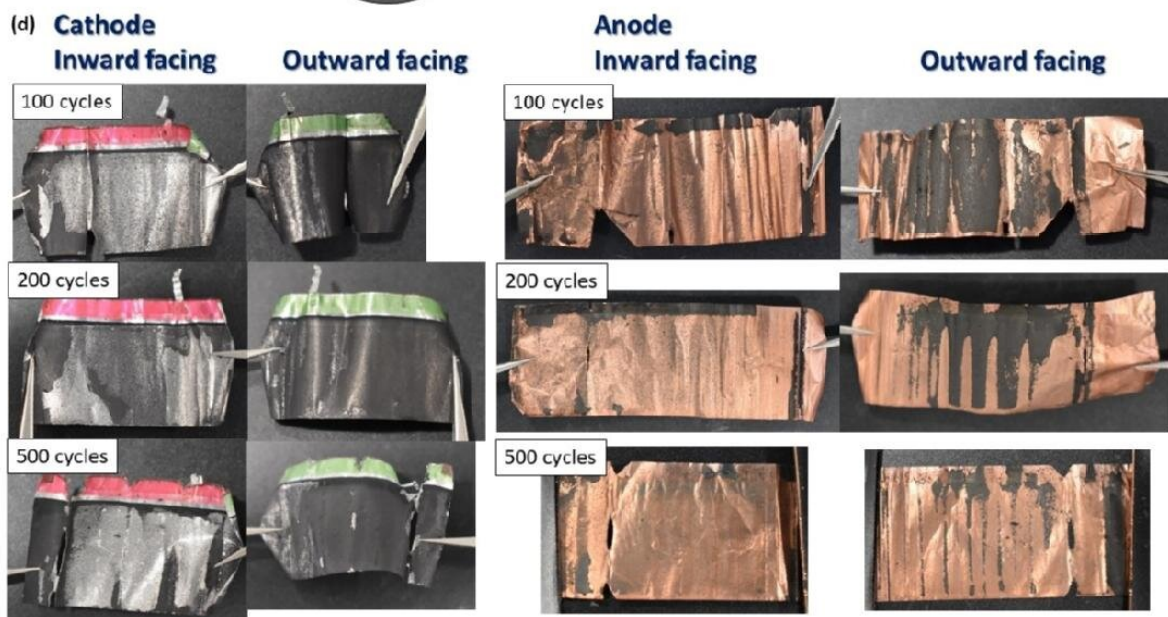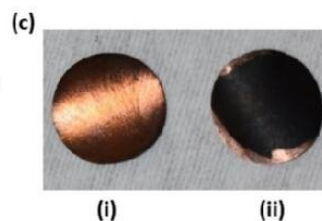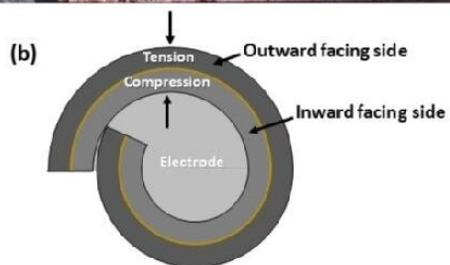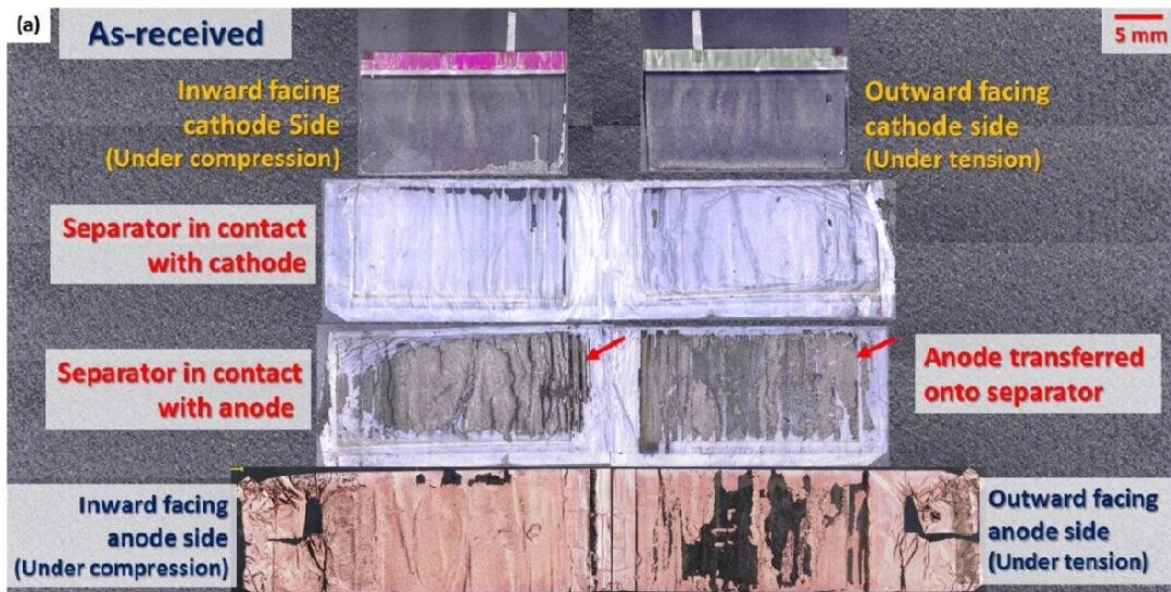

An image demonstrating the stresses to anodes and cathodes after cycles. Credit: University of Warwick

The inward facing cathode (under compression) when rolled into a jelly-roll, develops significant signs of [coating](#) delamination from the aluminum foil. On the outward facing cathode side (under tension), however, only a partial delamination was evident and the coating was transferred unto the separator. By contrast, severe delamination was observed on both sides of the anode coating. The inward facing anode side (under compression) showed almost no coating still adherent to the copper foil, compared to the outward facing anode side (under tension). Likewise, the delaminated coating had become adhered to the separator during operation.

Dr. Mel Loveridge from WMG, University of Warwick, says, "It is interesting to note that, for both the cathode and the anode, the delamination is more severe on the electrode coating side that would have been subjected to compression stress, rather than tensile strain. This can be further explained by considering the asymmetric forces in place on either side of double side coated electrodes."

The research team also carried out electrochemical testing, X-ray photoelectron spectroscopy (XPS), X-ray computed tomography (XCT) and scanning electron microscopy (SEM), to reveal the battery's structural features and changes. They found that it maintains 82% cell capacity after 500 continuous charging and discharging, after which it shows severe delamination due to high bending stress exerted on the cell components. However this seemingly has minimum impact on the electrochemical performance if the coating is sufficiently compressed in

the jelly roll with a good electrical contact. After aging, the surface layers continue to grow, with more LiF found on the [cathode](#) and [anode](#).

Their research opens up exciting areas in battery manufacturing to address winding issues for cylindrical cells (especially miniaturized formats). For example, highlighting the need to understand whether there is merit in varying the coating properties on each side of double-sided coating for wound cylindrical [cells](#), in order to improve the mechanical resilience of coatings that have asymmetric stresses exerted on them.

**More information:** C.C. Tan et al. Aging analysis and asymmetric stress considerations for small format cylindrical cells for wearable electronic devices, *Journal of Power Sources* (2020). [DOI: 10.1016/j.jpowsour.2020.228626](#)

Provided by University of Warwick

Citation: Improving battery life for wearable electronic devices by addressing asymmetric stresses (2020, August 25) retrieved 3 May 2024 from <https://techxplore.com/news/2020-08-battery-life-wearable-electronic-devices.html>

<p>This document is subject to copyright. Apart from any fair dealing for the purpose of private study or research, no part may be reproduced without the written permission. The content is provided for information purposes only.</p>
--